

Clear, High Thixotropic Wood Glaze Formulation

with Borchers Performance Additives

Raw Material	Supplier	Function	% by wt (clear)
WorléeKyd L 7904	Worlée	Linseed oil based alkyd resin	40.65
WorléeThix SD 6051	Worlée	Thixotropic long oil alkyd resin	25.00
Octa-Soligen® Calcium 10, basic	Milliken	Feed-Dryer	1.00
Borchers® AF 1171	Milliken	Defoamer	0.20
Borchi® OXY Coat 1310	Milliken	High-Performance Catalyst	1.00
White Spirit D60	VWR	Solvent	31.15
Borchi® Nox 1640	Milliken	Anti-Skinning	1.00
Total			100.00

Borchers Performance Additives

Borchi® OXY-Coat 1310:

Cobalt-free high-performance catalyst for thixotropic solvent borne systems

Borchers® AF 1171:



Polysiloxane, VOC-free defoamer for solvent borne and waterborne systems

Octa-Soligen® Calcium 10, basic:

Auxiliary drier, 2-ethylhexanoic acid-free


Borchi® Nox 1640:

MEKO-free anti-skinning agent for solvent borne systems

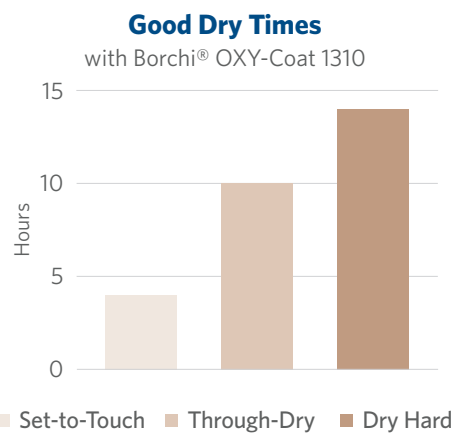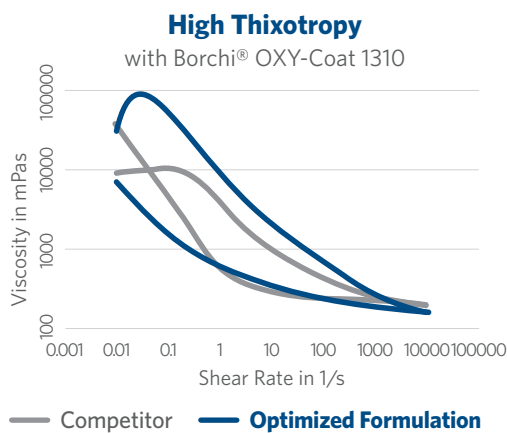

No Microfoam or Macrofoam

with Borchers® AF 1171

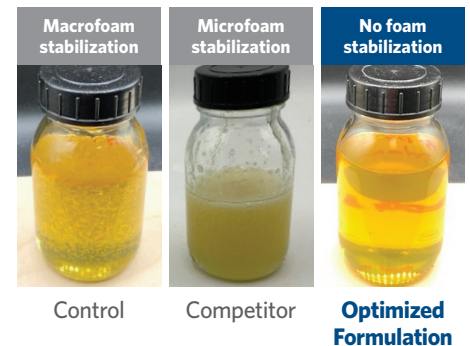

For more information, please reach us at borchers.com/contact

PLEASE NOTE: As each customer's use of our product may be different, information we provide, including without limitation, recommendations, test results, samples, care/labeling/processing instructions or marketing advice, is provided in good faith but without warranty and without accepting any responsibility/liability. Each customer must test and be responsible for its own specific use, further processing, labeling, marketing, etc. All sales are exclusively subject to our standard terms of sale posted at www.milliken.com/terms (all additional/different terms are rejected) unless explicitly agreed otherwise in a signed writing. Borchi is a trademark of Borchers Americas.

THIXWOOD-02.03.2025

Milliken